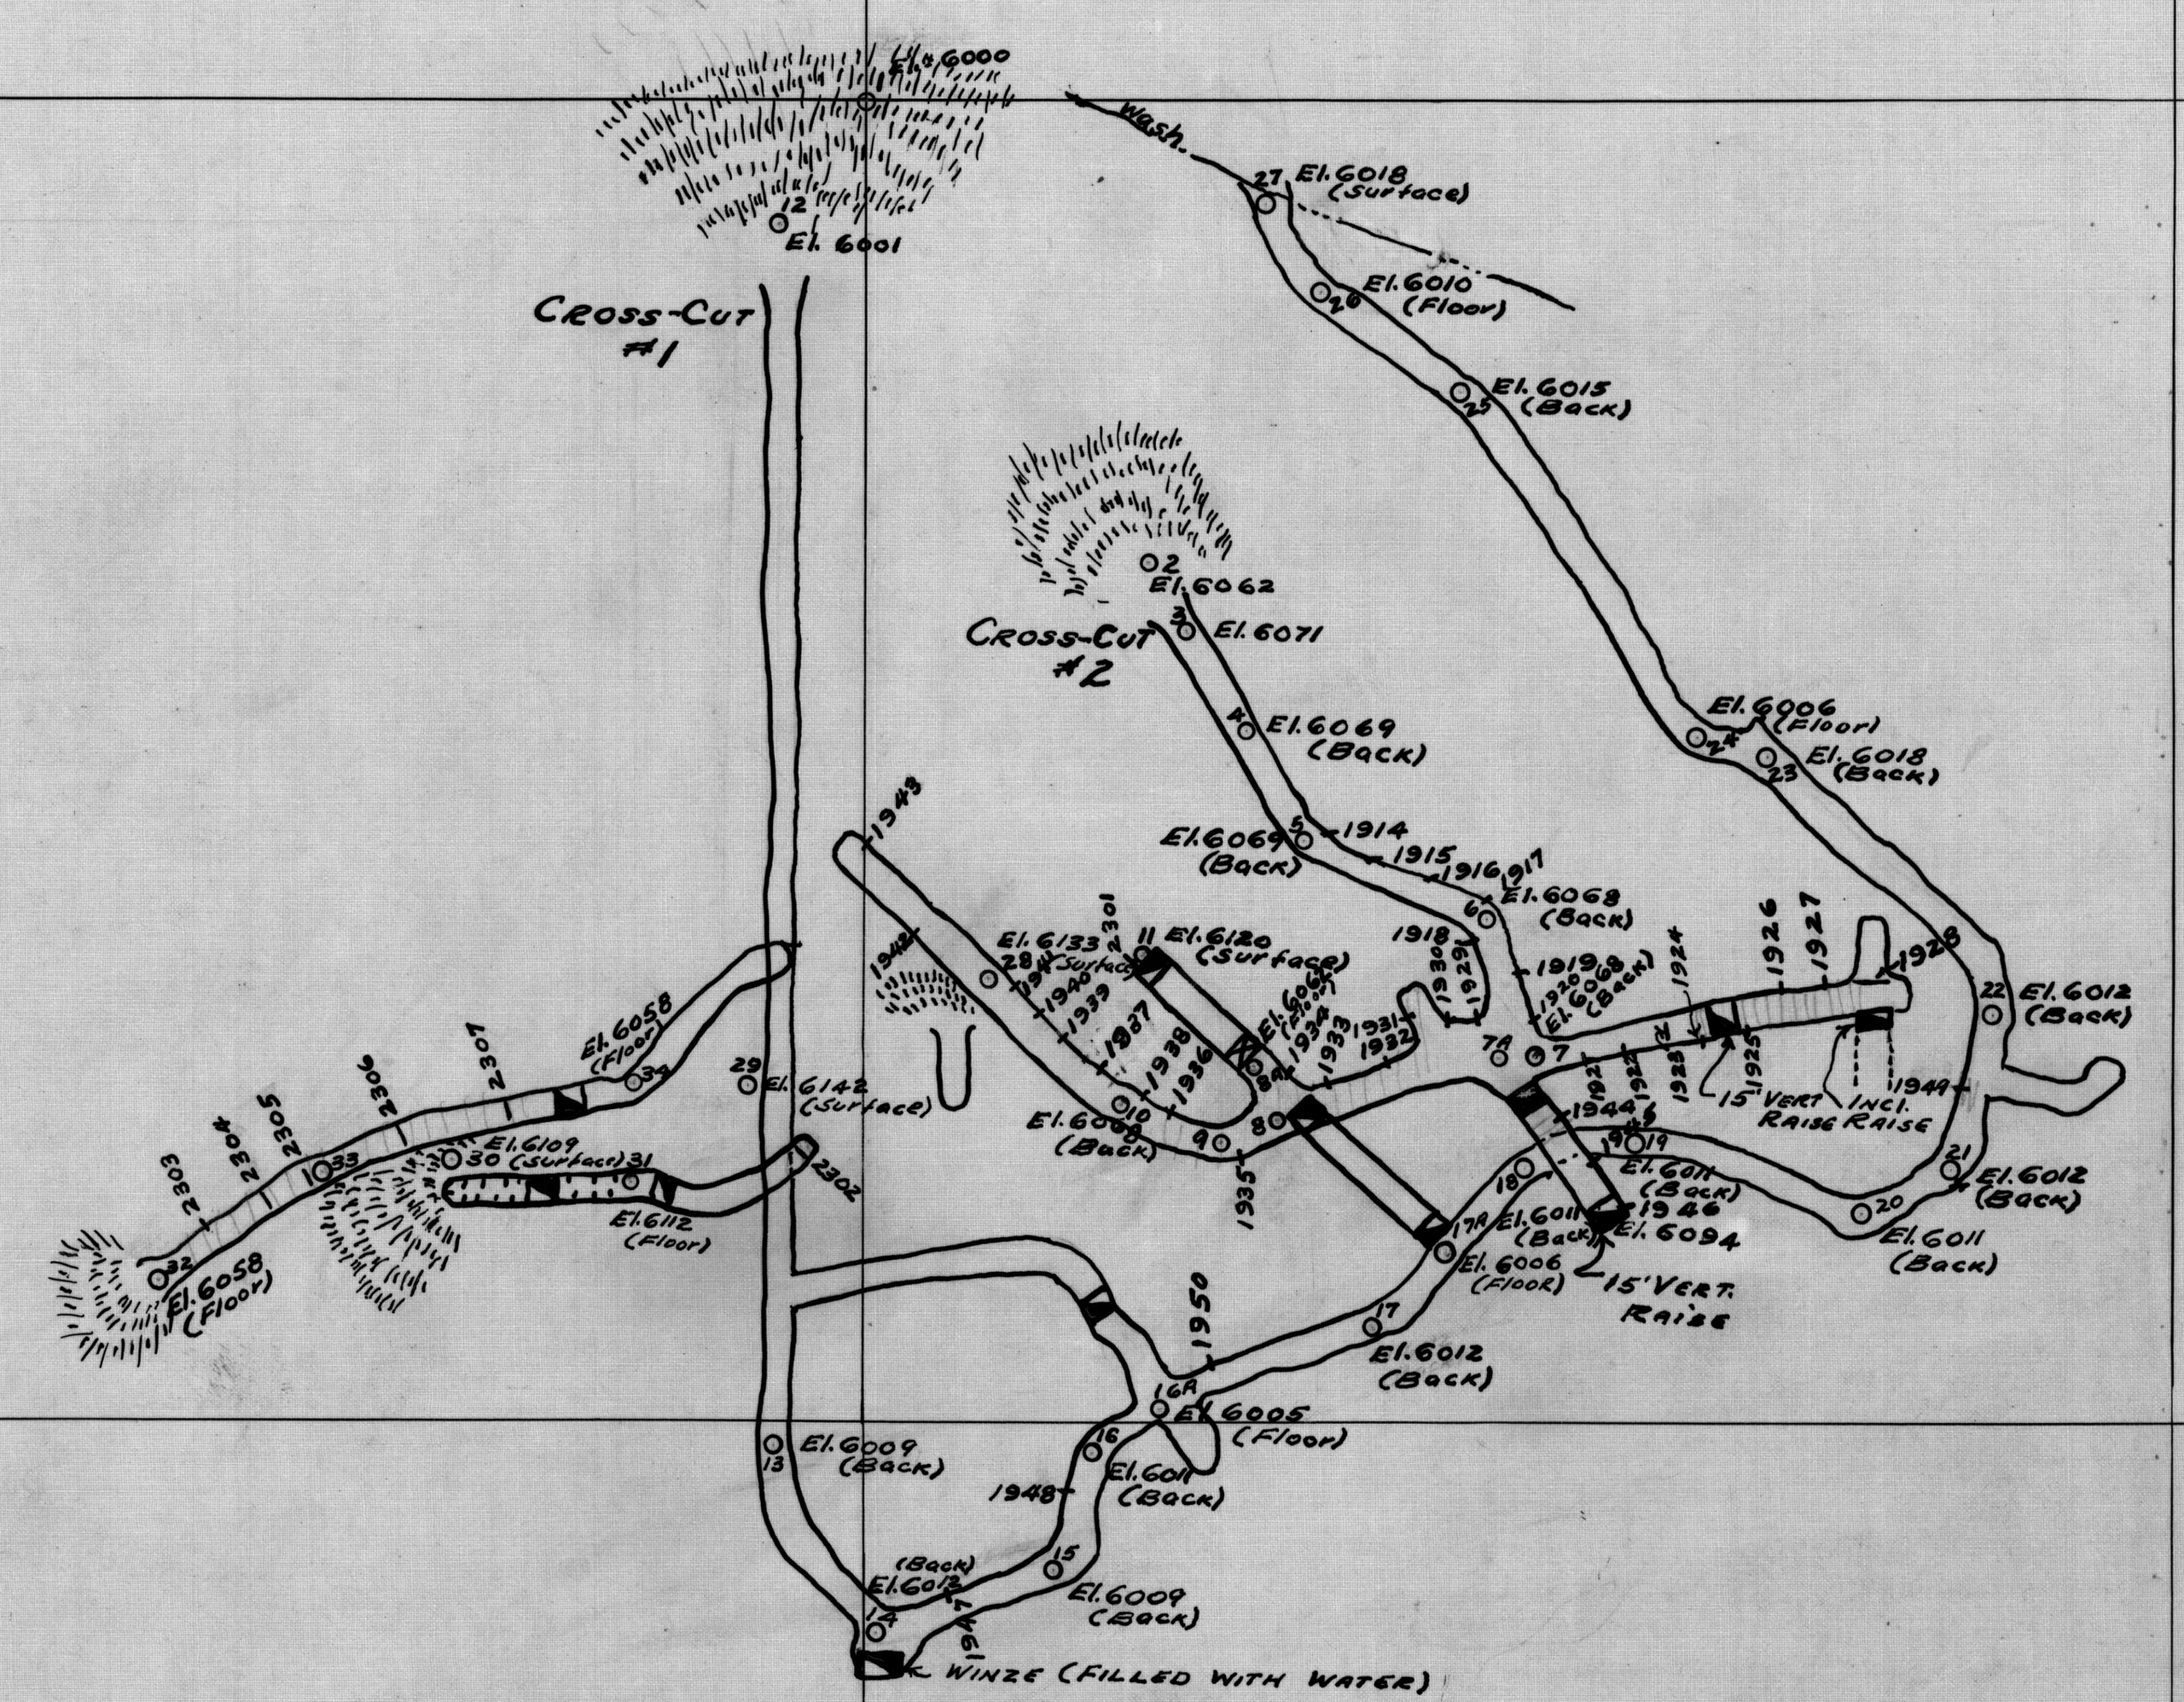

El 5904

N 1400

N 1200

N 900

N 600

N 300

0

E 300

E 600

E 900

E 1200

E 1500

E 1900

SAMPLE NO.	LENGTH	DESCRIPTION	% Zn.	% Cu.	% Pb	Ozs Ag.
1914	2.3'	Oxidized Gouge & Breccia		0.38		0.15
1915	2.0'	Partially Oxidized		2.61		1.15
1916	4.0'	Gouge & Breccia		1.21		0.50
1917	1.5'	Silic. Breccia, Sl. Miner.		0.52		0.10
1918	2.8'	Gouge & Breccia		2.29		0.70
1919	1.8'	Breccia, Partially Oxidiz		1.16		0.25
1920	7.0'	Silic. Partially Oxidized	4.4	1.66	6.7	5.55
1921	3.0'	Sulfides, Qtzite.		1.55		0.65
1922	4.0'	Sulfides; Diorite		1.90	2.0	4.35
1923	4.0'	Sulfides, Qtzite.			2.0	0.20
1924	7.0'	Sulfides, Tactite	1.4	2.44		4.75
1925	2.0	Gouge & Breccia		1.91		1.80
1926	2.5'	Sulfides, Tactite		3.28	5.0	7.25
1927	2.5'	Sulfides, Tactite		5.29	5.9	6.70
1928	5.8'	Gouge & Breccia		1.68		1.20
1929	6.0'	Siliceous L.S., Sulfides	1.4	1.32	2.0	1.75
1930	5.5'	Siliceous L.S., Sulfides		1.15		1.60
1931	3.0'	Oxidized Gouge & Breccia		2.02		1.65
1932	6.5'	Oxidized Gouge & Breccia		6.48		2.80
1933	3.0'	Gouge & Breccia, Sulfides		4.01	2.5	1.95
1934	3.0'	Gouge & Breccia, Sulfides		5.36	1.2	1.70
1935	1.0'	Oxidized Gouge & Breccia		2.96	1.2	2.95
1936	2.0'	Sil. Breccia & Gouge, FeS		5.18		1.75
1937	2.0'	Sil Breccia & Gouge, FeS		2.60		1.35
1938	3.0'	Quartzite; Sulfides		1.99		0.45
1939	6.5'	Diorite; Sulfides		1.96		0.70
1940	6.0'	Diorite; Sulfides, Chiefly FeS				0.50
1941	6.0'	Fractured Qtzite; Sulfides				0.30
1942	4.8'	Tactite & Diorite; Sulfides		0.37	1.1	2.60
1943	4.5'	Diorite & Qtzite; Sulfides			1.1	1.60
1944	5.5'	Silic. L.S.; Heavy Sulfides	9.6	4.46	6.0	2.05
1945	4.5'	Tactite; Light Sulfides	1.4			0.30
1946	4.0'	Tactite & Diorite; Sulfides	1.9		3.7	1.75
1947	2.5'	Quartzite; Light Sulfides		0.97		0.15
1948	5.5'	Siliceous L.S.; Sulfides		0.92		0.35
1949	2.0'	Siliceous L.S.; Sulfides		3.10		0.85
1950	5.0'	Quartzite; Sulfides		1.76		0.90
2301	4.0'	Silic. Breccia; Highly Oxidized		1.45		0.10
2302	2.5'	Highly Oxidized Gouge & Breccia		3.20		2.35
2303	5.0'	Highly Oxidized L.S. Breccia		3.34		0.75
2304	2.5'	Highly Oxidized Gouge & Breccia		1.88		0.50
2305	3.0'	Highly Oxidized Gouge & Breccia		3.31		1.00
2306	3.5'	Highly Oxidized Breccia		4.11		2.85
2307	2.0'	Highly Oxidized Gouge & Breccia		3.65		1.80

Notes:
Elevation at Sta. 1, assumed 6000 ft.
North coordinate line true north, determined by Brunton Compass.

LEGEND
- Raise
- Collar of winze & shaft
- Bottom of shaft
- Open cut

ASSAY MAP

HARTMAN HOMESTAKE - COPPER LEAD ZINC MINE

SCALE: 1" = 50'

See File 463.2 14035